



Scotch-Weld™ Structural Adhesive Primer EW-5000 AS

Technical Data

May, 2006

Product Description

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS is a sprayable, low VOC, heat curing, structural adhesive primer that contains a non-chromated, corrosion inhibiting package to provide protection against corrosive environments. Scotch-Weld EW-5000 AS primer is designed to provide ambient temperature drying with handleability right after spraying. Scotch-Weld EW-5000 AS primer meets the South Coast Air Quality Management District (SCAQMD) Rule 1124 VOC limit with less than 250 g per liter.

Key Features

- Non-chromate corrosion inhibiting package for corrosion protection
- VOC less than 250 g/L (meets SCAQMD Rule 1124)
- Can be sprayed to target thickness, 0.20 - 0.25 mil (5 - 6 μm), within one box coat (2 passes)
- Handleable prior to the bake cycle (no pre-bake required)
- Uses conventional spraying and drying (curing) equipment
- Shop friendly application characteristics
- Thickness range for performance: 0.12 - 0.40 mil (3 - 10 μm)
- Hot/Wet durability
- Pre-bake thickness can be checked by a gauge or a color chart
- Can be brush applied

Technical Data

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS

Typical Uncured Physical Properties

Note: The following technical information and data is based upon limited 3M testing conditions and should not be used for specification purposes.

Color:	Green
Base:	Epoxy
Vehicle:	Distilled water and small amounts of co-solvents
Solid Content:	31 ± 1%
VOC with Exempt Solvents:	225 g/L (calculated)
Net Weight:	8.9 lbs/gallon (1.06 g/cc)
Storage:	35-45°F (1-7°C) [DO NOT FREEZE]

Typical Cured Physical Properties

Note: The following technical information and data is based upon limited 3M testing conditions and should not be used for specification purposes.

I. Key Specifications

Appearance:	Glossy to Semi-Glossy
Air Dry Tack:	None
Pencil Hardness:	>7H ¹
40 Day Salt Spray Exposure:	Pass ²
Min. Thickness to MEK Resistance:	0.10 - 0.12 mil (2.5 - 3.0 μ) ³
Max. Thickness for Peel Performance:	0.40 - 0.42 mil (10.0 - 10.7 μ) ⁴

II. Wide Area Shear

Adhesive: 3M™ Scotch-Weld™ Structural Adhesive Film AF 163-2M, .06 wt.

Adhesive Cure: 250°F (121°C) – 90 minutes – 50 psi (3.45 x 10⁵ Pa) – 5.8°F/min rise rate (3.2°C/min).

Primer Cure: 30 min air dry followed by 60 min bake at 250°F (121°C).

Primer Thickness: 0.20 - 0.25 mil (5 - 6 μ).

- 67°F (-55°C)	5800 psi (40 MPa)
75°F (24°C)	5800 psi (40 MPa)
180°F (82°C)	4100 psi (28 MPa)
250°F (121°C)	2200 psi (15 MPa)
75°F (24°C) after 30 days at 100% RH / 120°F (49°C)	5500 psi (38 MPa)
75°F (24°C) after 30 days salt spray 95°F (35°C)	5700 psi (39 MPa)
75°F (24°C) after 7 days in jet fuel	5700 psi (39 MPa)
75°F (24°C) after 7 days in Skydrol® at 150°F (65°C)	5900 psi (41 MPa)

Tested according to ASTM D3165, crosshead speed of .05 in/min.


¹Tested according to ASTM D3363.

²No degradation on primer or metal was found beyond the scribe lines with both 2024 T3 bare and Alclad substrates. An example of a 40-day exposed panel.

2024 T3 Bare Aluminum Alloy; Phosphoric anodized; Primer thickness: 0.14 mil; The scribes were machine made with width of 0.062 in; Tested according to ASTM B117.

³Tested according to ASTM D5402.

⁴See metal-to-metal climbing drum peel data Section III of Typical Cured Physical Properties.

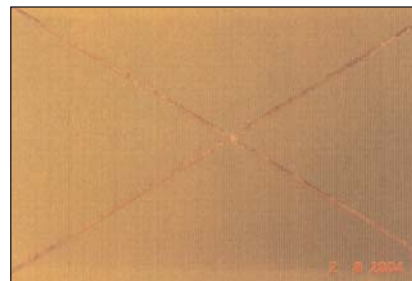

Technical Data

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS

Typical Cured Physical Properties (continued)

Note: The following technical information and data is based upon limited 3M testing conditions and should not be used for specification purposes.

III. Metal/Metal Climbing Drum Peel

Adhesive: 3M™ Scotch-Weld™ Structural Adhesive Film AF 163-2OST, .06 wt.
 Adhesive Cure: 250°F (121°C) – 90 minutes – 50 psi (3.45 x 10⁵ Pa) – 5.8°F/min rise rate (3.2°C/min).
 Primer Cure: 30 min air dry followed by 60 min bake at 250°F (121°C).
 Primer Thickness: 0.20 - 0.25 mil (5 - 6 μ).

Primer Thickness Mil (μ)	Peel Strength In-lb/in (mm-Kg/mm)	Adhesive Cohesive Failure Mode
0.26 (6.6)	83.5 (37.9)	100%
0.29 (7.4)	87.8 (39.8)	100%
0.31 (7.9)	84.8 (38.5)	100%
0.35 (8.9)	85.6 (38.8)	100%
0.36 (9.1)	83.5 (37.9)	98%
0.37 (9.4)	82.6 (37.4)	100%
0.38 (9.7)	77.1 (35.0)	100%
0.40 (10.2)	80.9 (36.7)	99%
0.42 (10.7)	85.4 (38.7)	98%
0.47 (11.9)	84.3 (38.2)	97%

The results are averages from several separate tests. Tested according to ASTM1781 except at crosshead speed of 3 in/min (76 mm/min).

IV. Flatwise Tensile

Adhesive: 3M™ Scotch-Weld™ Structural Adhesive Film AF 163-2M, .06 wt.
 Adhesive Cure: 250°F (121°C) – 90 minutes – 50 psi (3.45 x 10⁵ Pa) – 5.8°F/min rise rate (3.2°C/min).
 Core: 1/4" cell, 0.625" thick, PAA treated 5052 alloy, 4-mil foil, non-perforated.
 Primer Cure: 30 min air dry followed by 60 min bake at 250°F (121°C).
 Primer Thickness: 0.20 - 0.25 mil (5 - 6 μ).

75°F (24°C)	1600 psi (11 MPa)
180°F (82°C)	860 psi (5.9 MPa)
250°F (121°C)	160 psi (1.1 MPa)

Tested according to ASTM C297; Test speed was set so as to produce failure within 3-6 min.

V. Honeycomb Peel

Adhesive: Scotch-Weld AF 163-2M, .06 wt.
 Adhesive Cure: 250°F (121°C) – 90 minutes – 50 psi (3.45 x 10⁵ Pa) – 5.8°F/min rise rate (3.2°C/min).
 Primer Cure: 30 min air dry followed by 60 min bake at 250°F (121°C).
 Primer Thickness: 0.20 - 0.25 mil (5 - 6 μ).

75°F (24°C)	79 in-lb/3-in (910 mm-Kg/76-mm)
75°F (24°C) after 30 days at 100% RH / 95°F (35°C)	80 in-lb/3-in (920 mm-Kg/76-mm)
75°F (24°C) after 30 days salt spray 95°F (35°C)	80 in-lb/3-in (920 mm-Kg/76-mm)

Tested according to ASTM1781 except at crosshead speed of 3 in/min (76 mm/min).

Technical Data

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS

Typical Cured Physical Properties (continued)

Note: The following technical information and data is based upon limited 3M testing conditions and should not be used for specification purposes.

VI. Other Performance Tests

Adhesive Cure: 250°F (121°C) – 90 minutes – 50 psi (3.45 x 10⁵ Pa) – 5.8°F/min rise rate (3.2°C/min).

Primer Cure: 30 min air dry followed by 60 min bake at 250°F (121°C).

Primer Thickness: 0.20 - 0.25 mil (5 - 6 μ).

Tests	Adhesive	Test Condition	Results
Wedge Crack ¹	3M™ Scotch-Weld™ AF163-2K .06WT	100% RH / 140°F (60°C) for 7 days	100% cohesive failure, crack length less than 0.25 in (6 mm)
Slow Cycle Fatigue	3M™ Scotch-Weld™ AF163-2M .06WT	100% RH / 140°F (60°C); 1500 psi (10.3 MPa); 5 cycles/hr	> 1700 cycles
Fatigue ²	3M™ Scotch-Weld™ AF163-2M .06WT	Ambient condition; 30 Hz at 1500 psi (10.3 MPa)	> 2x10 ⁶ cycles

¹Tested according to ASTM D3762.

²Tested according to ASTM D3166.

Product Application

Note: This information is provided as a general application guideline based upon typical conditions. No two applications are identical due to differing assemblies, method of heat and pressure application, production equipment and other limitations. It is therefore suggested that experiments be run, within the actual constraints imposed, to determine optimum conditions for your specific application and to determine suitability of product for particular intended use.

I. Surface Preparation

A thoroughly cleaned, dry, and grease free surface is essential for maximum performance. Cleaning methods which will produce a break free water film on metal surfaces are generally satisfactory.

The best performance will be achieved with the surface preparation by alkaline (e.g. Oakite™ 164 or Isoprep™ 44 solutions) degreasing, then FPL etching, according to ASTM D2674, and followed by phosphoric acid anodizing, according to ASTM D3933.

II. Agitation

Always mix well before transferring 3M™ Scotch-Weld™ Adhesive Primer EW-5000 AS to the spray system. Mixing can be achieved by the following operations:

1. **Roller mixer.** Place the primer on the roller mixer, and let it roll for 20 minutes.
2. **Mechanical stirrer.** Use a propeller type blade. Stir at medium low speed (100 - 150 rpm) for 15 - 20 minutes.
3. **Paint shaker.** Use with caution. Do not shake for more than 5 minutes. Otherwise excessive foam can form.

Technical Data

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS

Product Application (continued)

Note: This information is provided as a general application guideline based upon typical conditions. No two applications are identical due to differing assemblies, method of heat and pressure application, production equipment and other limitations. It is therefore suggested that experiments be run, within the actual constraints imposed, to determine optimum conditions for your specific application and to determine suitability of product for particular intended use.

III. Spray Procedure

1) Equipment and settings:

Spray Equipment	Conventional HVLP spray gun ¹ , e.g. 3M™ PPS™ Paint Preparation System HVLP Spray Gun Part #16212 ² Accuspray® Series 12 HVLP Spray Gun Binks® Mark 1 HVLP Spray Gun
Fluid and Air Nozzle	1.3 mm or less for siphon or gravity feed guns 1.0 mm or less for pressure feed guns
Atomizing Pressure	6 - 10 psi (40 - 69 kilopascal) at the air cap (gun tip) ³
Fluid Nozzle Setting	1/2 - 3/4 turn out from close position
Fan Pattern	Adjust fan pattern control to provide about 45 - 60 spray pattern
Gun Distance	6 - 12 inch (15 - 30 cm) from the panel

¹Can be either a siphon or gravity-feed gun.

²PPS Part #16212 comes with a kit that contains a fluid nozzle of 1.3 mm tip.

³For 3M™ PPS™ Paint Preparation System Spray Gun, set the pressure just below the purple zone at the gauge attached to the gun.

2) Spray Process

- Make sure to let the primer warm up to ambient temperature before spray. Preferably 65°F (18°C) or higher, but not to exceed 95°F (35°C).
- The spray of water-borne products varies with temperature and humidity conditions. To assure good spray appearance, the booth temperature should be above 70°F (21°C), and humidity should be below 50%.
- For best post-cured appearance, allow flash-off between passes. At high humidity and low temperature conditions, spray less material each pass, and allow extra passes to achieve the designated thickness.
- A training DVD is available through your 3M Aerospace Sales Representative.

IV. Primer Dry and Cure

Air Dry 30 minutes at 75 ± 5°F (24 ± 3°C), followed by
Cure 60 minutes at 250 ± 5°F (121 ± 3°C)

V. Primer Thickness

Optimal thickness:^{1,2} 0.15 - 0.25 mil (3.8 - 6.4 μm) after cure.

¹Primer thickness can be measured after the primer has flash dried, yet before bake. If thickness is measured before bake, about 0.02 - 0.05 mil (0.5 - 1.2 μm) shrinkage will occur after bake.

²The recommended thickness should be achieved within 2 to 3 passes (or 1 to 1.5 box coats) depending on temperature and humidity. One box coat is defined as two passes, perpendicular to each other.

Technical Data

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS

Storage

3M™ Scotch-Weld™ Structural Adhesive Primer EW-5000 AS should be stored at refrigerated conditions, e.g. 35-45°F (1-7°C). DO NOT FREEZE. The shelf life under this condition is 1 year from date of shipment.

Scotch-Weld EW-5000 AS primer should be permitted to thoroughly warm to room temperature in a sealed container before being used in order to provide its normal spray and drying characteristics. However, do not expose it to temperatures above 100°F (38°C) for a prolonged period of time.¹

The out time of Scotch-Weld EW-5000 AS primer is 30 days under 80°F (27°) and 7 days at 90°F (32°C).

¹The primer should not be exposed for more than 24 hours at 100°F (38°C) and should not be exposed for more than 1 hour at 120°F (49°C).

Precautionary Information

Refer to Product Label and Material Safety Data Sheet for health and safety information before using this product. For additional health and safety information, call 1-800-364-3577 or (651) 737-6501 or visit www.3M.com/msds.

For Additional Information

To request additional product information or to arrange for sales assistance, call toll free 1-800-235-2376 or fax 1-800-435-3082 or 651-737-2171. For U.S. Military, call 1-866-556-5714 or fax 651-737-4380. If outside of the U.S., please contact your nearest 3M office.

Important Notice

3M MAKES NO WARRANTIES, EXPRESS OR IMPLIED, INCLUDING, BUT NOT LIMITED TO, ANY IMPLIED WARRANTY OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE. User is responsible for determining whether the 3M product is fit for a particular purpose and suitable for user's method of application. Please remember that many factors can affect the use and performance of a 3M product in a particular application. The materials to be bonded with the product, the surface preparation of those materials, the product selected for use, the conditions in which the product is used, and the time and environmental conditions in which the product is expected to perform are among the many factors that can affect the use and performance of a 3M product. Given the variety of factors that can affect the use and performance of a 3M product, some of which are uniquely within the user's knowledge and control, it is essential that the user evaluate the 3M product to determine whether it is fit for a particular purpose and suitable for the user's method of application.

Limitation of Remedies and Liability

If the 3M product is proved to be defective, THE EXCLUSIVE REMEDY, AT 3M'S OPTION, SHALL BE TO REFUND THE PURCHASE PRICE OF OR TO REPAIR OR REPLACE THE DEFECTIVE 3M PRODUCT. 3M shall not otherwise be liable for loss or damages, whether direct, indirect, special, incidental, or consequential, regardless of the legal theory asserted, including, but not limited to, contract, negligence, warranty, or strict liability.

AS9100

This product was manufactured under a 3M quality system registered to AS9100 standards.

3M

Aerospace and Aircraft Maintenance Department

3M Center, Building 223-1N-14
St. Paul, MN 55144-1000
www.3M.com/aerospace



Recycled Paper
40% pre-consumer
10% post-consumer

3M is a trademark of 3M Company.
Oakite is a trademark of Chemetall Oakite Products, Inc.
Isoprep is a trademark of MacDermid Incorporated.
AccuSpray is a registered trademark of AccuSpray Application Technologies, Inc.
Binks is a registered trademark of ITW Industrial Finishing.
Skydrol is a registered trademark of Solutia, Inc.
Printed in U.S.A.
©3M 2006 60-9700-0115-6 (5/06)